

Magnetic Field Induced Density of States in Superconducting MgB_2 : Measurement of Conduction Electron Spin-Susceptibility

F. Simon^{1,2}, A. Jánossy¹, T. Fehér^{1,2}, F. Murányi¹, S. Garaj², L. Forró², C. Petrovic^{3,*}, S. Bud'ko³, R. A. Ribeiro³, P. C. Canfield³

¹*Budapest University of Technology and Economics,*

Institute of Physics and Solids in Magnetic Fields Research Group of the Hungarian Academy of Sciences, H-1521 Budapest, PO BOX 91, Hungary

²*IPMC, École Polytechnique Fédérale de Lausanne, CH-1015 Lausanne, Switzerland*

³*Ames Laboratory, U.S. Department of Energy and Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011*

(Dated: February 2, 2008)

The magnetic field dependence of the spin-susceptibility, χ_s was measured in the superconducting state of high purity MgB_2 fine powders below 1.3 T. χ_s was determined from the intensity of the conduction electron spin resonance spectra at 3.8, 9.4, and 35 GHz. At the lowest magnetic fields (0.14 T), a gap opens in the density of states at the Fermi energy and, accordingly, $\chi_s(T)$ is small at low temperatures. Fields above 0.2 T (about 15 % of H_{c2}^c , the minimum upper critical field), destroy the gap. The field induced χ_s is much larger than expected from current superconductor models of MgB_2 .

PACS numbers: 74.70.Ad, 74.25.Nf, 76.30.Pk, 74.25.Ha

It is now generally accepted that MgB_2 is a phonon mediated superconductor[1][2][3] which owes its unusual properties to the widely different electron-phonon couplings on its disconnected Fermi surface (FS) sheets[4]. The two-gap model assumes a large superconductor gap for the cylindrical sheets originating from B-B σ bonds and a smaller gap for the FS sheet of π electrons. It describes physical properties such as the temperature dependent specific heat [5] and tunneling[6] successfully in zero magnetic field, predictions in finite fields are much less tested. Recent experiments show that magnetic fields as low as $H_{c2}^\pi \approx 1$ T close the smaller, π -gap[7][8][9][10]. The stronger electron-phonon coupling for σ electron states maintains the superconductivity above 1 T. Yet, there has been no microscopic description of this phenomenon. The cylinder-like FS sheets of the σ bands are responsible for the anisotropy of the upper critical field, $H_{c2}^{ab} = 16$ T and H_{c2}^c about 2.5 T[11][12][13]. Band calculations[4] estimate that about half of the density of states (DOS) is on the π band thus the two-gap model predicts that closing the gap at 1 T restores about half of the normal state DOS. Naively, one would expect that properties proportional to the DOS, like the specific heat coefficient or the spin-susceptibility should reach half of their normal state values at about 1 T, whereas the remaining half originating from the σ bands should be restored gradually with further increasing the field to H_{c2} .

In this Letter, we report on the magnetic field dependence of the conduction electron spin-susceptibility, χ_s , in the superconducting state of high purity MgB_2 powders. This is the first time χ_s is measured using conduction electron spin resonance below T_c in a superconductor. We observe an unusually strong increase of χ_s with the magnetic field, H , which cannot be reconciled with current models easily. The DOS induced by fields well below H_{c2} is larger than 50 %, the value expected from

closing the gap on the π band FS only.

We studied samples from several batches. Sample 1 is made from 99.99 % purity natural isotopic mixture of ^{10}B and ^{11}B amorphous boron, Samples 2 and 3 are made from crystalline, isotopically pure ^{11}B . Chemical analysis, the high normal state conductivities and narrow CESR lines at T_c attest the high purity of the samples. Details of sample characterization are discussed in Ref. [14]. Sample 2 was made from the batch used in the CESR work of Ref. [11]. Fine powders with grain sizes less than 1 μm were selected from the starting materials to reduce the inhomogeneity of microwave excitation. The aggregates of small grains of the starting materials were first thoroughly hand-crushed in a borocarbide mortar. The resulting powders were suspended in isopropanol and mixed in a 1:1 weight ratio with pure SnO_2 fine powder. The larger particles were eliminated by sedimentation for long times or in a centrifuge and the small grains were extracted from the suspension by filtering. Mixing with SnO_2 is important to separate the MgB_2 particles to avoid eddy-currents. SEM microscopy has confirmed that this procedure results in MgB_2 grains smaller than 0.5 μm size. SQUID magnetometry of the original batch and the final fine powders confirmed that superconducting properties were not affected by this procedure. The powders were finally cast into epoxy for the ESR experiments. We detail CESR experiments at 3.8, 9.4 and 35 GHz at fields near 0.14, 0.34 and 1.28 T respectively. The CESR results at higher frequencies of Ref.[11] were also reproduced and we confirmed that the minimum value of the higher upper critical field, H_{c2}^{min} , is somewhat below 2.7 T. χ_s of MgB_2 was measured from the intensity of the CESR with no need for core electron corrections. Fine powder of the air stable metallic polymer, $o\text{-KC}_{60}$ was mixed into the epoxy for some of the samples to serve as a temperature independent ESR in-

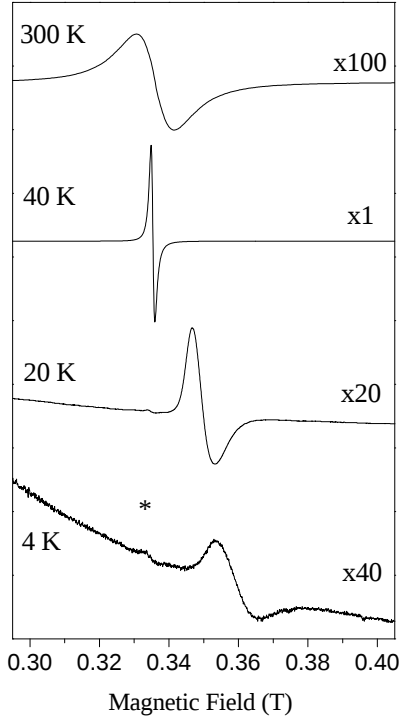


FIG. 1: Temperature dependence of the CCSR signal of MgB₂ fine powder sample (Sample 1) at 9.4 GHz (0.34 T). * denotes the ESR signal of a tiny amount of paramagnetic impurity phase

tensity standard [15]. Intensity measurements at 9 GHz (where instrumental factors are well controlled) with and without KC₆₀ were consistent. The absolute value of χ_s was measured against a secondary CuSO₄·5 H₂O standard at 9.4 GHz.

Figure 1 shows the CCSR spectra at 9.4 GHz for Sample 1. The room temperature peak-to-peak linewidth, $\Delta H_{pp}=111\pm3$ G, of the derivative absorption line is dominated by spin-lattice relaxation due to phonons. The residual linewidth at 40 K arises from static imperfections and is sample dependent. The residual linewidth is somewhat smaller for Sample 1 ($\Delta H_{pp}=10\pm0.3$ G), than for Sample (2,3), (11 ± 0.3 and 20 ± 0.6 G) while the residual resistance ratio (RRR) is larger for the latter two samples [14]. Unlike the RRR, the CCSR linewidth is insensitive to intergrain scattering and the difference may be related to the different morphology of Sample 1 and (2,3). The small asymmetry of the lineshape ($A/B=1.16$ for Sample 1) at 40 K shows that microwave penetration is nearly homogeneous[16], the nominal particle size is in the range of the microwave penetration depth, $\delta=0.3$ μ m, and the reduction of the CCSR signal intensity due to screening is less than 5 %.

Above 450 K (data not shown), the CCSR intensities are the same for the three samples and correspond to a susceptibility of $\chi_s=(2.3\pm0.3)\cdot10^{-5}$ emu/mol in agreement with the previously measured value[11] of $\chi_s=(2.0\pm0.3)\cdot10^{-5}$ emu/mol and calculations of the

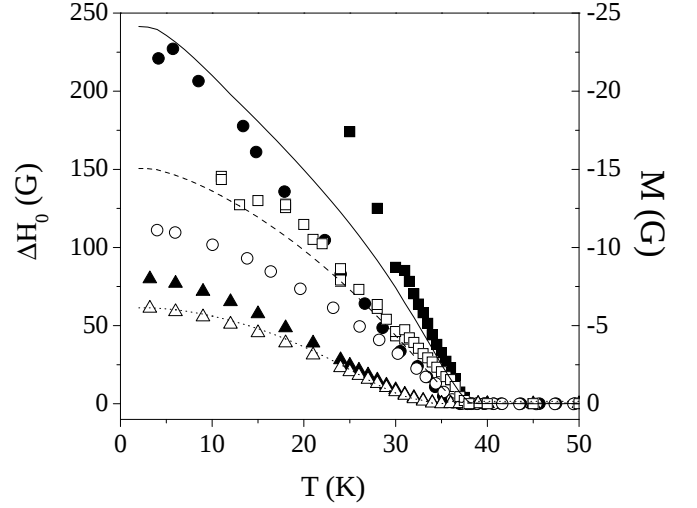


FIG. 2: Temperature dependence of the diamagnetic shift (full symbols are up, open symbols are down sweeps) of the CCSR (squares: 3.8 GHz, 0.14 T; circles: 9.4 GHz 0.34 T; triangles: 35 GHz, 1.28 T) and diamagnetic magnetization measured by SQUID (solid, dashed, and dotted curves are at 0.14, 0.34, and 1.28 T, respectively).

DOS[3]. In Sample 1, the CCSR intensity is nearly T independent in the normal state, the measured small decrease of about 20 % between 600 and 40 K is of the order of experimental precision at high temperatures. In Sample 2 and 3 the CCSR intensity decreased by a factor of 2.5 between 450 and 40 K. The nearly symmetric Lorentzian lineshape showed that this intensity decrease is not due to a limited penetration depth. Neither does the intensity decrease correspond to a change in χ_s . We measured the T dependence of the ¹¹B spin-lattice relaxation time, T_1 , in Samples 2 and 3 and found a metallic, T independent value of $1/(TT_1)=167\pm3$ s⁻¹ in agreement with Ref. [17] and [18]. It is possible that the difference in morphology and purity at the grain surfaces explains that the CCSR signal intensity is almost constant in Sample 1 while it changes strongly in Sample 2 and 3. We believe that the nearly constant CCSR intensity and the constant $1/(TT_1)$ measures correctly the metallic susceptibility of MgB₂.

Below T_c , the T and H dependence of the diamagnetic shifts, linewidths, and intensities normalized at T_c are similar in all three samples. We discuss Sample 1, for which the CCSR signal intensity is constant in the normal state within experimental precision. For the applied magnetic fields, $H < H_{c2}^{min}(T = 0 \text{ K})$ and at $T \ll T_c$ the CCSR signal corresponds to the mixed state of the MgB₂ superconductor; any non-superconducting fraction would be easily detected as in Ref.[11] for $H > H_{c2}^{min}$. The ESR of a tiny impurity phase is well outside the CCSR of MgB₂ (marked by * in Fig. 1). Comparison of the diamagnetic magnetization, M , measured by SQUID and the diamagnetic shift of the CCSR, $\Delta H_0(T) = H_0(T) - H_0(40 \text{ K})$ (H_0 is the resonance field), also verifies

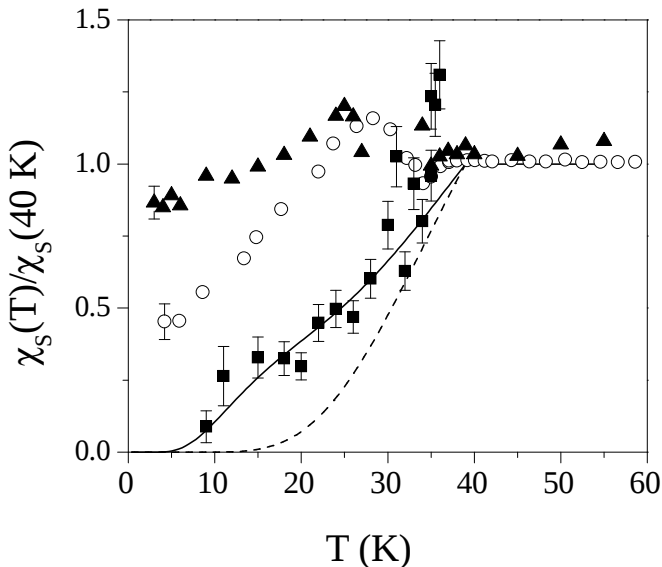


FIG. 3: The temperature and magnetic field dependent spin-susceptibility of MgB₂ below T_c (squares: 3.8 GHz, 0.14 T; circles: 9.4 GHz 0.34 T; triangles: 35 GHz, 1.28 T). Dashed and solid curves are calculated χ_s for an isotropic BCS and a two-gap model as explained in the text, respectively.

that below T_c we detect the CESR of the MgB₂ superconductor. Figure 2 shows $\Delta H_0(T)$ at 3 different ESR frequencies and M at the corresponding static magnetic fields with a scaling between ΔH_0 and M as in Ref.[11]. The present diamagnetic shift data on fine grain samples at 35 GHz and higher frequencies (not shown) agrees with our previous report on large grain samples[11]. $\Delta H_0(T)$ is equal to the average decrease of the applied magnetic field in the sample and is proportional within a shape dependent constant to M of the grains. $\Delta H_0(T)$ averaged for increasing and decreasing field sweeps is proportional to M in the field cooled sample with the same proportionality constant in a broad range of T 's for all the three magnetic fields. We used the same argument previously to identify the signal of superconducting MgB₂ particles in higher frequency (>35 GHz) CESR experiment[11].

The CESR line broadens inhomogeneously below T_c due to the macroscopic inhomogeneities of diamagnetic stray fields (data not shown). Within each isolated grain, spin diffusion motionally averages all magnetic field inhomogeneities arising from screening currents or vortices[19] and the modulation of field between vortex cores does not broaden the CESR. The line is however broadened in the randomly oriented powder by the crystalline and shape anisotropy of the diamagnetic shift, that changes from grain to grain. As expected for this case, the observed additional linewidth in the superconducting state, ΔH_a , is proportional to the shift and $\Delta H_a/\Delta H_0(T)$ is about 0.3 at all fields and temperatures.

The main topic of the current report is the measurement of χ_s in the superconducting state of MgB₂. Usually, χ_s is determined from the measurements of tem-

perature dependent Knight's shift or spin-lattice relaxation time, T_1 [20]. To our knowledge, in MgB₂ there has been no successful determination of these quantities below T_c : precision of the Knight's shift measurement is limited due to the diamagnetic magnetization[17][21], while T_1 measurements are affected by several factors like vortex motion[17]. In CESR, the signal intensity is proportional to χ_s and diamagnetism affects only the shift of the resonance line. χ_s is proportional to the DOS of normal excitations when electron correlations are small.

In Figure 3, we show χ_s below 60 K measured at three magnetic fields. The 9.4 GHz (0.34 T) and 35 GHz (1.28 T) data are normalized at 40 K while the 3.8 GHz (0.14 T) data are normalized at 100 K. At 3.8 GHz and 35 GHz data are missing in ranges of 36 to 100 K and 27 to 34 K, respectively, where the CESR of MgB₂ could not be resolved from the KC₆₀ reference. Data taken at 9.4 GHz with and without reference agree well and the data without reference are shown. Irreversibility does not affect the measurement of χ_s in the studied range of T and H : linewidths and shifts depend on the direction of the field sweep at low T but the intensities are the same within 5 % that is our experimental precision at low T . In Fig. 3, data at 9.4 and 35 GHz are averaged for sweeps with increasing and decreasing fields while at 3.8 GHz decreasing field sweep data are shown. No correction is made for diamagnetic screening of the microwave excitation, this would increase somewhat further the measured values of χ_s .

The T dependent χ_s at our lowest magnetic field, 0.14 T, lies well above $\chi_s^0(T, H=0)$ (dashed curve in Fig. 3) calculated for an isotropic $T_c=39$ K weak coupling BCS superconductor[22]. The measured χ_s at 0.14 T is compatible with the two gap model above 10 K. The solid curve in Fig. 3 shows $\chi_s(T, H=0)$ calculated within the model of two independent gaps. We used $\Delta_1(T=0)=11$ K and $\Delta_2(T=0)=45$ K, with DOS equally shared on the two Fermi surfaces, and both gaps opening at T_c . The choice of these parameters is in agreement with experimental results [5][6][23] and theoretical estimates[4].

The remarkably large field induced χ_s observed at 0.34 and 1.28 T at all T 's below T_c is the main finding of this work. These fields are much smaller than the upper critical fields, $H_{c2}^c \sim 2.5$ T [11][12][13] and $H_{c2}^{ab} \sim 16$ T. Unlike in usual superconductors, χ_s at $T_c/2$ is still near to its normal state value and remains large at the lowest T 's; $\chi_s(4\text{ K})/\chi_s(40\text{ K}) = 0.46 \pm 0.06$ at 0.34 T and $\chi_s(3\text{ K})/\chi_s(40\text{ K}) = 0.87 \pm 0.06$ at 1.28 T. As shown in Fig. 4, the measured χ_s at low T is in rough agreement with the specific heat[5][24] measured on a powder sample (solid curve in Fig. 4) but we find an even stronger field dependence. The specific heat data, unlike the χ_s data, are affected by the electron-phonon enhancement which varies strongly between the different FS sheets. The data cannot be described by a simple anisotropic superconductor. The dashed curve in Fig. 3 shows the calculated field dependence of χ_s of a powder of an anisotropic superconductor with $H_{c2}^c=2$ T and $H_{c2}^{ab}=16$ T at $T=0$. Here,

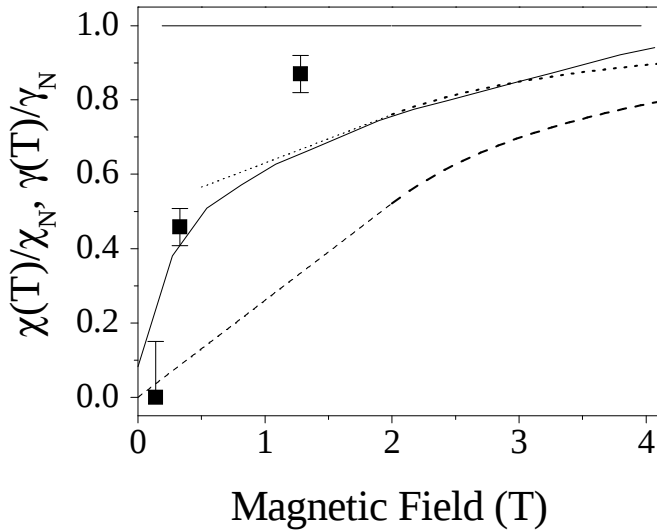


FIG. 4: Comparison of the normalized χ_s/χ_N at 4 and 3 K at 0.34 and 1.28, respectively (squares) and the normalized specific heat coefficient γ/γ_N (solid line) at 3 K from Ref. [24]. Dashed curve shows H dependent DOS for an anisotropic $H_{c2}^c = 2$ T, $H_{c2}^{ab} = 16$ T superconductor. Dotted curve is a similar superconductor, but with half of the DOS restored by 0.5 T. For 16 T, all curves merge at 1.

we assumed a Landau-Ginzburg type angular dependence of $H_{c2}(\theta)$ as described in Ref.[11] and a contribution to χ_s proportional to $H/H_{c2}(\theta)$ for each superconducting grain. As seen in Fig. 4, this description is inadequate. A better approximation is obtained if, following Ref. [7] [8][9], one assumes that the π band FS is restored at

around $H \sim 1$ T and the observed anisotropic H_{c2} arises solely from the σ band. In Fig. 4 we show this case with dotted lines, assuming that 50 % of the DOS is already restored at $H = 0.5$ T. However, this simple minded application of the two-gap model is still inadequate: the large value of χ_s at 1.28 T and 3 K, and the T dependence at 0.34 T, in particular the restoration of the full DOS at 25 K, remain unexplained.

In conclusion, the magnetic field dependence of the spin-susceptibility in MgB_2 shows that a large part of the Fermi surface is restored at fields well below the minimum of the upper critical field. These observations pose a challenge to theory since they cannot be explained with an anisotropic superconductor model nor by simple application of the two-gap model even if it is assumed that the π band FS is restored at magnetic fields as low as $0.1 \cdot H_{c2}^{\min}$.

Support from the Hungarian State Grants, OTKA T029150, OTKA TS040878, and FKFP 0352/1997 and the NCCR network MANEP of the SNSF are acknowledged. The authors are grateful to Silvija Gradečak and Csilla Mikó for the SEM experiments and to Edina Couteau for assistance in the fine powder preparation. FS and TF acknowledge the Bolyai Hungarian Research Fellowship for support. TF acknowledges the hospitality of the Grenoble High Magnetic Field Laboratory during the NMR measurements. Ames Laboratory is operated for the U.S. Department of Energy by Iowa State University under Contract No. W-7405-Eng-82.

* Present address: Department of Physics, Brookhaven National Laboratory, Upton, New York 11973

-
- [1] J. Nagamatsu *et al.*, Nature, **410**, 63 (2001).
 - [2] S. L. Bud'ko *et al.*, Phys. Rev. Lett. **86**, 1877 (2001).
 - [3] J. Kortus *et al.* Phys. Rev. Lett. **86**, 4656 (2001).
 - [4] A. Y. Liu, I. I. Mazin, J. Kortus, Phys. Rev. Lett. **87**, 087005 (2001).
 - [5] F. Bouquet *et al.*, Phys. Rev. Lett. **87**, 047001 (2001).
 - [6] P. Szabó *et al.*, Phys. Rev. Lett. **87**, 137005 (2001).
 - [7] F. Bouquet *et al.*, Phys. Rev. Lett. **89**, 257001 (2002).
 - [8] M. R. Eskildsen *et al.*, Phys. Rev. Lett. **89**, 187003 (2002).
 - [9] R. S. Gonnelli, *et al.*, Phys. Rev. Lett. **89**, 247004 (2002).
 - [10] P. Szamuely, *et al.*, cond-mat/0211544.
 - [11] F. Simon *et al.*, Phys. Rev. Lett. **87**, 047002 (2001).
 - [12] S. L. Bud'ko, V. G. Kogan and P. C. Canfield, Phys. Rev. B **64**, 180506 (2001).
 - [13] S. L. Bud'ko and P. C. Canfield, Phys. Rev. B **65**, 212501 (2002).
 - [14] R. A. Ribeiro, S. L. Bud'ko, C. Petrovic, P. C. Canfield, Physica C(Amsterdam) **382**, 194 (2002).
 - [15] F. Bommeli *et al.*, Phys. Rev. B **51**, 14794 (1995).
 - [16] F. J. Dyson, Phys. Rev. **98**, 349 (1995).
 - [17] J. K. Jung *et al.*, Phys. Rev. B., **64** 012514 (2001).
 - [18] H. Kotegawa *et al.*, Phys. Rev. Lett. **87**, 127001 (2001).
 - [19] P. G. de Gennes, Solid State Comm., **4**, 95 (1966).
 - [20] C. P. Slichter, Principles of Magnetic Resonance, Springer Verlag, (New York) 1990.
 - [21] A. P. Gerashenko *et al.*, Appl. Magn. Res. **21**, 157 (2001).
 - [22] Kei Yosida, Phys. Rev. **110**, 769 (1958).
 - [23] F. Bouquet *et al.*, Europhys. Lett. **56**, 856 (2001).
 - [24] A. Junod *et al.*, cond-mat/0106394; F. Bouquet *et al.*, Physica C(Amsterdam) **385**, 192 (2003).